



Synthesis and mesomorphic properties of new heterocyclic liquid crystals with Central Ester–Chalcone linkages

Yong-Wei Cheryl Lim^a, Sie-Tiong Ha^{a,*}, Guan-Yeow Yeap^b, S. Sreehari Sastry^c

^a Department of Chemical Science, Faculty of Science, Universiti Tunku Abdul Rahman, Jln Universiti, Bandar Barat, 31900 Kampar, Perak, Malaysia

^b Liquid Crystal Research Laboratory, School of Chemical Sciences, Universiti Sains Malaysia, 11800 Minden, Penang, Malaysia

^c Department of Physics, Acharya Nagarjuna University, Nagarjuna Nagar, 522 510, India

Received 19 November 2015; received in revised form 14 December 2015; accepted 15 December 2015

Available online 29 December 2015

Abstract

A series of new calamitic liquid crystals, 4-[3-(pyridin-4-yl)prop-2-enoyl]phenyl 4-alkoxybenzoates, comprising a pyridyl core, ester–chalcone central linkage and terminal alkoxy chain were synthesized and characterized. This series consists of four members that differ by the length of the alkoxy chain ($C_nH_{2n+1}O-$, where $n = 10, 12, 14, 16$). The structures of the title compounds were elucidated using spectroscopic and spectrometric techniques, such as FT-IR, NMR (1H and ^{13}C) and EI-MS. The mesomorphic properties were studied using differential scanning calorimetry and optical polarizing microscopy. The decyloxy-containing compound was found to be non-mesogenic, whilst the compounds containing *n*-dodecyloxy to *n*-hexadecyloxy chains exhibited an enantiotropic smectic A phase with a fan-shaped texture. From the structure–property relationship study, it was proposed that the number of carbons in the alkoxy chain must be at least 12 ($n \geq 12$) to generate the smectic phase in the corresponding substituted $ArCOOArCOCH=CHC_5H_4N$ compounds.

© 2015 The Authors. Production and hosting by Elsevier B.V. on behalf of Taibah University. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Keywords: Pyridyl; Chalcone; Smectic A; Mesomorphic

1. Introduction

The electronically conducting behaviour of liquid crystals (LCs) has received overwhelming attention

since the discovery of high hole mobility in the hexagonal columnar phase of hexapentyloxy-triphenylene liquid crystals [1–5]. Recently, calamitic LCs have been identified as another potential material for application in electronic devices due to the presence of some ordered mesophases, such as SmA, SmC, SmB, SmE, among others. The two-dimensional arrangement (i.e., layers) in smectics is more tolerant with regard to defects than the one-dimensional ordered discotic columns, resulting in enhanced electronic performance [6]. The electronically conducting behaviour of calamitic liquid crystals was first investigated in the SmA phase of 2-phenylbenzothiazole derivatives. The presence of


* Corresponding author.

E-mail addresses: hast_utar@yahoo.com, hast@utar.edu.my (S.-T. Ha).

Peer review under responsibility of Taibah University.



Production and hosting by Elsevier

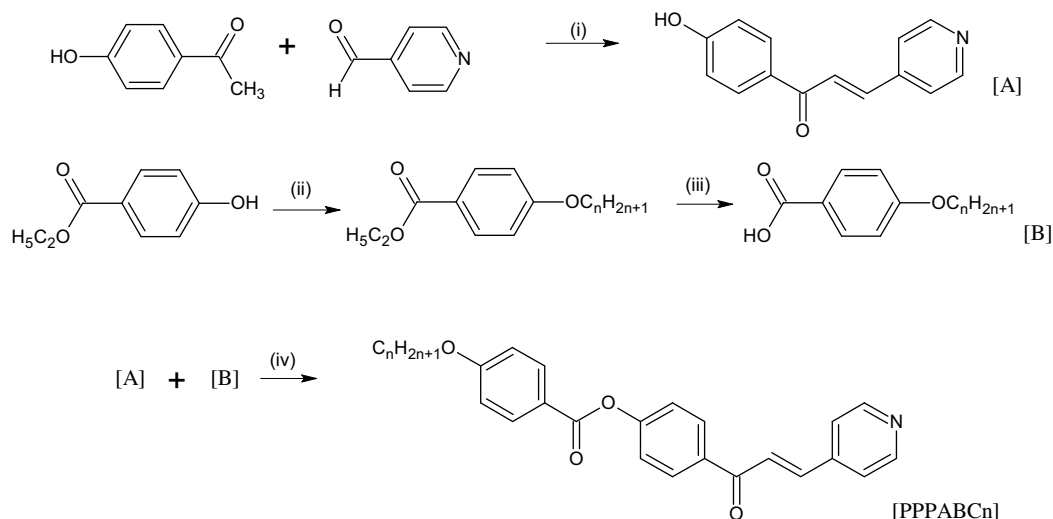

Scheme 1. Synthetic route for the target compounds. (i) KOH dissolved in EtOH:H₂O (1:1), 2 M HCl (ii) C_nH_{2n+1}Br, K₂CO₃, CH₃COCH₃ (iii) H₂O:EtOH (1:1), KOH, conc. HCl (iv) DCC, DMAP, DCM, DMF.

layer structures in all smectic liquid crystalline materials induces π – π stacking interactions that can facilitate the hopping of electrons, thereby increasing charge carrier mobility [7–9].

Our previous work focused on the synthesis of a few homologous series of smectic LCs containing a benzothiazole moiety [10–13]. Incorporation of a benzothiazole ring into calamitic liquid crystals as a mesogenic core enabled the resulting molecules to easily exhibit mesophases due to the more polarizable nature of the heteroatoms sulphur and nitrogen [14]. In this paper, we report a new homologous series of heterocyclic liquid crystals comprising a pyridyl unit (Scheme 1). Introduction of a nitrogen atom into the aromatic core results in a more complex mesomorphic behaviour. In a few cases, highly ordered smectic phases (e.g., G, H) are observed at or near room temperature, which are properties that are of interest, if the materials also possess useful charge mobilities for application in real devices.

Liquid crystals containing a chalcone central linkage are relatively rare. In the literature, there are several reports of mesogenic compounds having chalcone linkages. Many years ago, Chudgar and Shah [15] and Yeap et al. [16] reported a homologous series of mesogenic compounds containing ester-chalcone linkages. Recently, Thaker et al. [17] also synthesized mesomorphic compounds containing a Schiff base–chalcone linkage. The emergent scientific interest in the synthesis of heterocyclic liquid crystals and the outstanding liquid crystalline behaviour of chalcone-containing compounds has prompted us to synthesize a series of mixed pyridyl–chalcone liquid crystals. The presented molecules consist of three core units (one pyridyl and two

phenyl rings) connected via enone and ester linkers that can increase the molecular broadness and anisotropy.

2. Experimental

2.1. Characterization

Infrared spectroscopy was performed on a Perkin-Elmer System 2000 FT-IR Spectrometer. All compounds were analyzed using KBr discs with a measurement range of 4000 to 400 cm^{−1}. ¹H NMR (400 MHz) and ¹³C NMR (100 MHz) spectra were recorded in CDCl₃ using a JEOL LA-400 MHz NMR spectrometer with tetramethylsilane as the internal standard. EI-MS (70 eV) was measured with a Finnigan MAT95XL-T Mass Spectrometer at a source temperature of 200 °C.

Phase-transition temperatures and associated enthalpy changes were measured using a Mettler Toledo Differential Scanning Calorimeter DSC823^c at heating and cooling rates of 10 °C/min and −10 °C/min, respectively. A polarizing optical microscope (Carl Zeiss) equipped with a Linkam hotstage was used for temperature dependent studies of the liquid crystal textures. A video camera (Video Master coomo20P) installed on the microscope was attached to a video capture card (Video Master coomo600), allowing real-time video capture and image saving. The textures exhibited by the compounds were observed using polarized light with crossed polarizers. Samples were prepared as thin films sandwiched between a glass slide and a cover slip. Phase identification was made by comparing the observed textures with those reported in the literature [18,19].

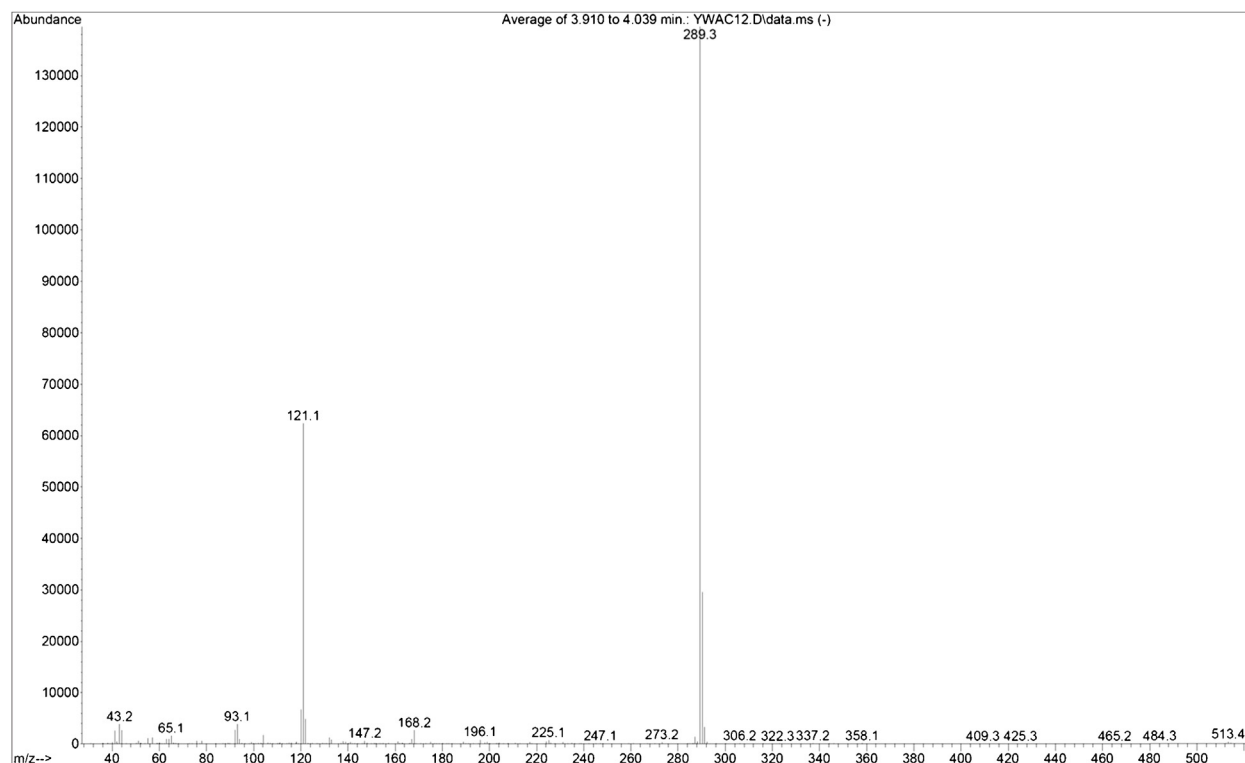


Fig. 1. EI-MS spectrum of PPPABC12.

2.2. Synthesis

All solvents and reagents were purchased commercially and used without any further purification. 4-Dimethylaminopyridine (DMAP), 4-hydroxyacetophenone, pyridine-4-carbaldehyde, 1-bromoalkane ($C_nH_{2n+1}Br$, where $n = 10, 12, 14, 16$), potassium hydroxide and potassium carbonate were obtained from Merck (Germany). Ethyl 4-hydroxybenzoate and N,N' -dicyclohexylcarbodiimide (DCC) were purchased from Acros Organics (USA).

The synthetic route for the formation of the title compounds, 4-[3-(pyridin-4-yl)prop-2-enoyl]phenyl 4-alkoxybenzoates (PPPABC n , where $n = 10, 12, 14, 16$), is illustrated in Scheme 1. Intermediate compounds 1-(4-hydroxyphenyl)-3-(pyridin-4-yl)prop-2-en-1-one and 4-alkoxybenzoic acid were prepared according to the method described by Ha and Low [20] and Kadkin et al. [21], respectively.

2.2.1. Synthesis of mixed pyridyl–chalcone liquid crystals

1-(4-Hydroxyphenyl)-3-(pyridin-4-yl)prop-2-en-1-one (2 mmol, 0.45 g), the appropriate 4-alkoxybenzoic acid (2 mmol) and DMAP (1 mmol, 0.12 g) were

dissolved in a 10-mL mixture of DCM and DMF, and the solution was stirred at 0 °C. DCC (2 mmol, 0.41 g) dissolved in 10 mL of DCM was added to the mixture dropwise, and the solution was continuously stirred for an hour at 0 °C. The mixture was then stirred at room temperature for 48 h. Finally, the mixture was filtered and the solvent was removed by evaporation. All of the crude products were purified by repeated recrystallizations using a 2:1 ratio of methanol and chloroform until constant melting points were obtained. The purity of all of the compounds was verified by thin layer chromatography (Merck 60 F₂₅₄) and visualized under short-wave UV light.

The IR, NMR (¹H and ¹³C) and mass spectral data for the representative compound, PPPABC12, are summarized as follows.

4-[3-(Pyridin-4-yl)prop-2-enoyl]phenyl 4-dodecyloxybenzoates (PPPABC12): IR ν_{max} (KBr, cm^{-1}): 2922, 2852 (C–H aliphatic); 1728 (C=O ester); 1662 (C=O keto), 1273 (C–O, aromatic ether). ¹H NMR (400 MHz, CDCl₃, δ ppm): 0.9 (t, 3H, CH₃–), 1.3–1.5 (m, 18H, CH₃–(CH₂)₉–(CH₂)₂–O–), 1.8 (p, 2H, –CH₂–CH₂–O–), 4.0 (t, 2H, –CH₂–O–), 7.0 (d, 1H, olefinic–H), 7.4 (d, 2H, Ar–H), 7.5 (d, 1H, olefinic), 7.6–7.7 (m, 4H, Ar–H), 8.1–8.2 (m, 4H, Ar–H), 8.7

Infrared data of PPPABC12 show the absorption bands assignable to the stretching of aliphatic C-H bonds in the frequency range of 2852 to 2946 cm^{-1} . The band appearing at 1728 cm^{-1} can be ascribed to the stretching of the C=O bond belonging to the ester group. Another C=O bond, observed at a lower frequency of 1662 cm^{-1} , is attributed to the keto group. Formation of

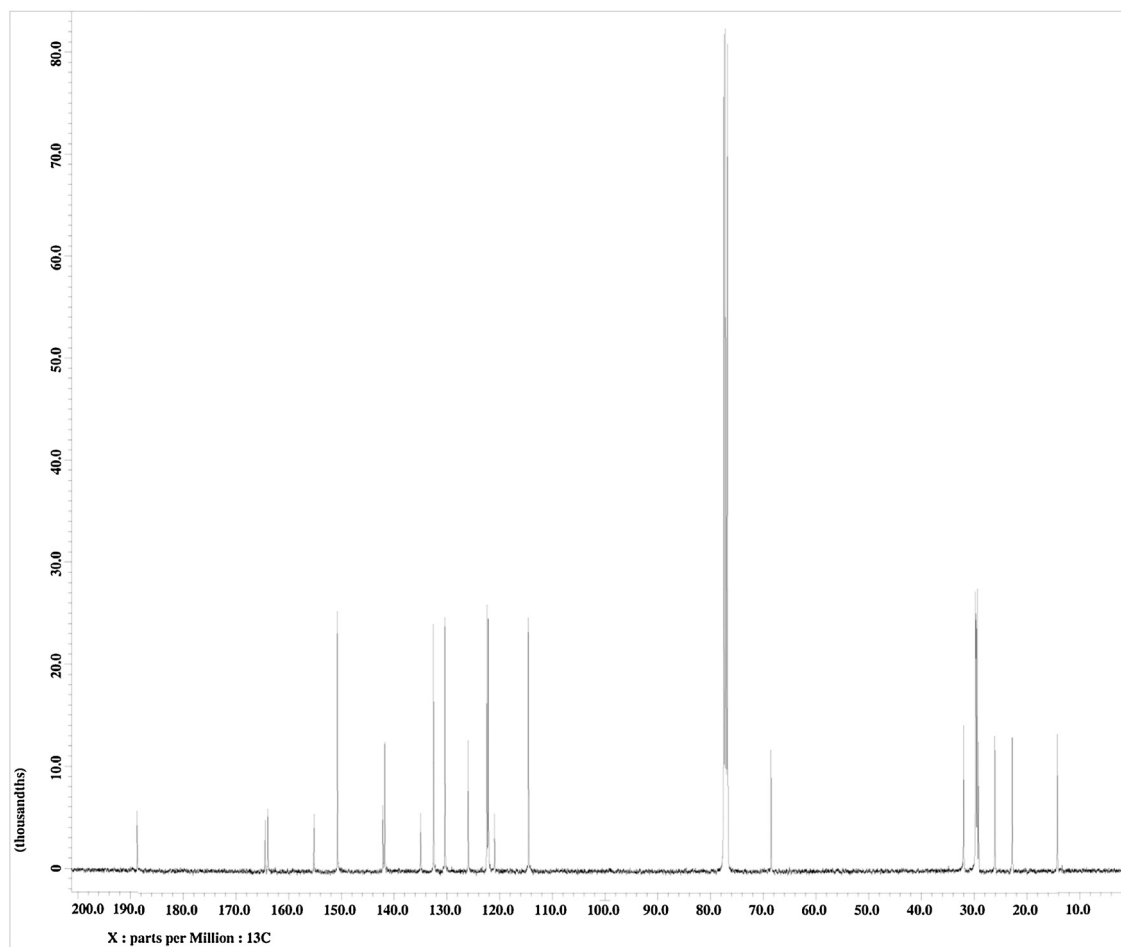


Fig. 3. ^{13}C NMR spectrum of PPPABC12.


the aromatic ether bond ($\text{C}-\text{O}-\text{Ar}$) was confirmed based on the absorption band at 1273 cm^{-1} .

Figs. 2 and 3 show the ^1H and ^{13}C NMR spectra, respectively, for PPPABC12. The ^1H NMR spectrum of PPPABC12 shows two triplets assignable to the methyl (CH_3) group of the ether linkage and methylene protons attached to the ether oxygen ($-\text{CH}_2-\text{O}-$) at δ 0.9 and δ 4.0, respectively. Triplet splitting was observed due the presence of two neighbouring protons in both cases. The other methylene protons of $\text{CH}_3-(\text{CH}_2)_9-(\text{CH}_2)_2-\text{O}-$ group in the alkyl chain were confirmed by the presence of multiplet signals at δ = 1.3–1.5. A pentet signal assignable to the methylene protons of the $\text{CH}_2\text{CH}_2\text{CH}_2\text{O}-$ group appears at δ 1.8. The presence of two olefinic protons is confirmed with the presence of doublets at chemical shifts of δ 7.0 and δ 7.4. Resonances attributable to the eight aromatic and four pyridyl protons were observed in the range of δ 7.4–8.7.


The molecular structure of PPPABC12 was further substantiated by ^{13}C NMR spectroscopy. The presence of the $\text{C}=\text{O}$ ester group can be corroborated by the ^{13}C signal observed at δ 164.45. The most downfield signal at δ 188.71 is assigned to the $\text{C}=\text{O}$ of the enone group. Signals attributable to the olefinic carbons can be found δ 122.38 and 141.77. The peaks belonging to the aromatic and pyridyl carbons gave ^{13}C signals between δ 114.52 and δ 163.95. The methylene carbon attached to the ether oxygen ($-\text{CH}_2\text{O}-$) possessed the highest chemical shift (δ 64.49) among the methylene carbons. The remaining carbons on the alkyl chain exhibited signals between δ 14.23 and δ 32.01.

3.2. Mesomorphic behaviour

The mesophases of all of the compounds were observed under an optical polarizing microscope during heating and cooling cycles. The optical

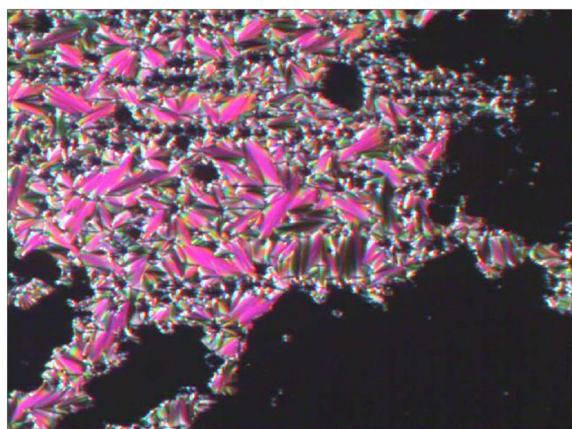

(a)

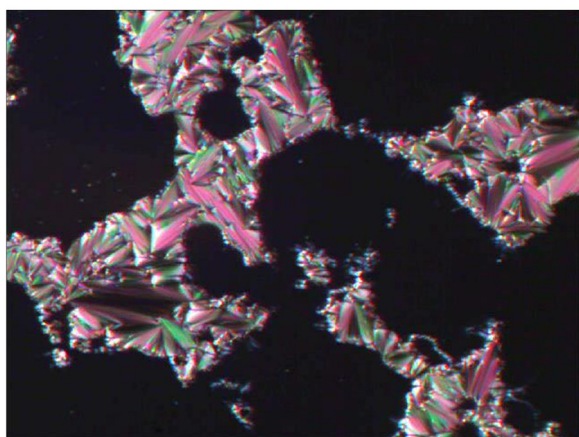

(b)

Fig. 4. Optical photomicrographs (100 \times) of (a) PPPABC12 and (b) PPPABC14 exhibiting smectic A phase with fan-shaped and homeotropic textures.

photomicrographs of PPPABC12 and PPPABC14 are depicted in Fig. 4 as a representative illustration. Upon cooling from an isotropic liquid, the co-existence of fan-shaped and homeotropic (dark area) textures of the smectic A (SmA) phase was observed for PPPABC12 (Fig. 4a) and PPPABC14 (Fig. 4b). All observed liquid crystalline textures are typical according to the literature [18,19].

The phase transition temperatures and corresponding enthalpy changes of the compounds PPPABC n were determined by differential scanning calorimetry (DSC). The data obtained from the DSC analysis are summarized in Table 1. The DSC thermogram (Fig. 5) of PPPABC14 shows two endotherms upon heating that can be attributed to the isotropic–mesophase and mesophase–crystal transitions. Such transitions were also supported by the enthalpy values of the respective compounds. It is clear from Table 1 that PPPABC14

Table 1

Phase transition and transition enthalpy changes for PPPABC n upon heating and cooling.

Compound	Phase transition, $^{\circ}\text{C}$ (corresponding enthalpy changes, kJ mol^{-1})
PPPABC10	Heating: Cr 115.8 (49.9) I Cooling: Cr 108.7 (49.6) I
PPPABC12	Heating: Cr ₁ 110.9 (44.1) Cr ₂ 118.8 (23.1) I Cooling: Cr 94.6 (57.8) SmA 111.5 (3.5) I
PPPABC14	Heating: Cr 109.8 (64.4) SmA 117.1 (4.6) I Cooling: Cr 98.2 (59.5) SmA 116.0 (2.5) I
PPPABC16	Heating: Cr 111.4 (41.8) SmA 118.1 (2.9) I Cooling: Cr 89.7 (41.6) SmA 115.8 (2.7) I

Cr, crystal; SmA, Smectic A; I, isotropic. Value in the bracket is enthalpy change.

and PPPABC16 exhibited enantiotropic properties, as the mesophases were observed during both heating and cooling cycles. All of the compounds exhibited a smectic A (SmA) phase, except for the *n*-decyloxy derivative (i.e., PPPABC10).

The linking group is one of the determining factors that influences whether the target compound will exhibit a smectic phase instead of a nematic phase. The ester linking group generally favours lamellar packing due to the dipole–dipole interaction, which ultimately generates the smectic phase [22]. In the case of PPPABC n , conjugation over the entire molecule was achieved between the enone linking group and pyridyl core system, which led to expression of the smectic phase. This suggests that the heteroatom of pyridyl group at the terminal position has a substantial effect on influencing certain phases. It has been reported that the inclusion of heteroatoms can significantly change the polarity, polarisability and occasionally the geometric shape of the molecule, thus influencing the type of mesophase, phase transition temperatures, dielectric and other properties of the mesogens [14]. Because of the presence of nitrogen in the pyridyl ring at the terminal position, these compounds may also serve as a new type of donor group for hydrogen bonding studies (e.g., $-\text{COOH} \cdots \text{N}-$) with acceptor molecules (for example, 4-alkyloxybenzoic acids) to form new binary liquid crystals [23–26].

As the length of the terminal chain increased, the phase changed from non-mesogenic to enantiotropic smectic A phase. The smectic character was absent in PPPABC10, but was present in the compounds containing longer alkyl chains (PPPABC12, 14, 16). PPPABC10, containing an *n*-decyloxy chain, is too rigid to be mesogenic, while longer terminal alkyloxy chains may favour a lamellar arrangement in smectic layer

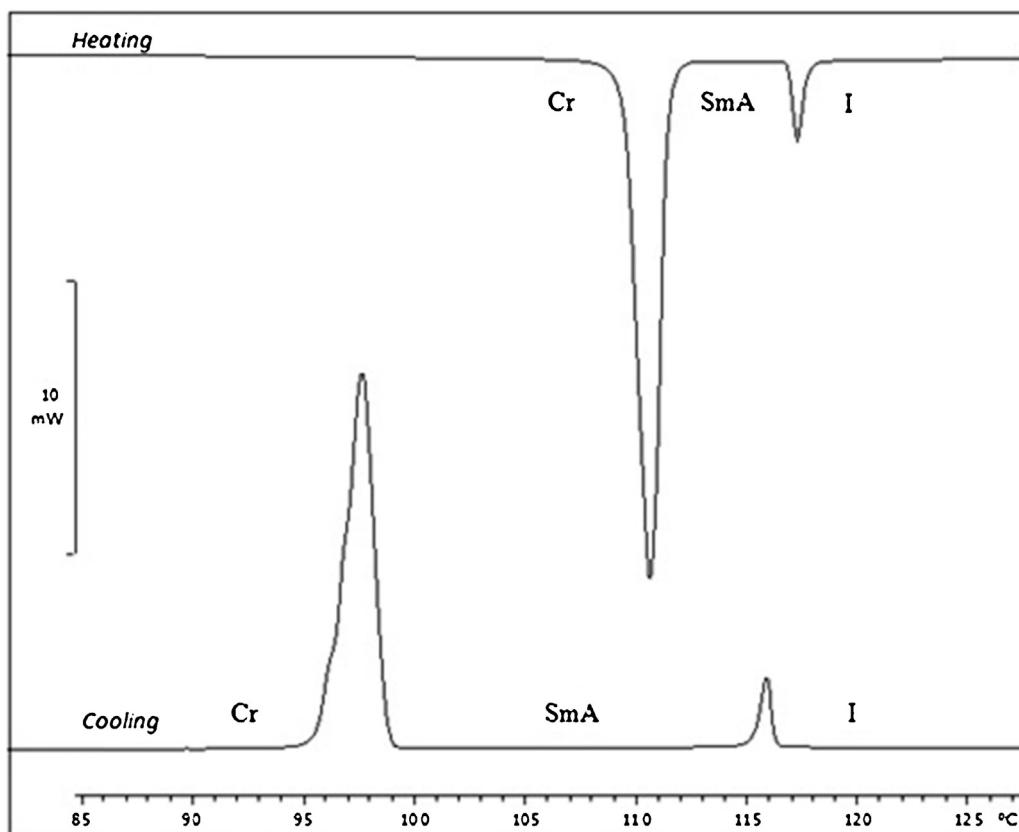


Fig. 5. DSC thermogram of PPPABC14 upon heating and cooling.

structures due to higher *Van der Waals* interactions and the possibility of intertwining between alkyloxy chains. It can therefore be proposed that to generate the smectic phase in the substituted $\text{ArCOOArCOCH=CHC}_5\text{H}_4\text{N}$ compounds, the number of carbons in the alkyloxy chain ($\text{C}_n\text{H}_{2n+1}\text{O-}$) must be at least 12 ($n \geq 12$). Lastly, the SmA phase range (Δ_{SmA}) was reduced as the chain length increased from C12 to C16, which could be due to dilution of the mesogenic core [27,28].

4. Conclusion

In this paper, we have described the synthesis and mesomorphic behaviour of a new homologous series of 4-[3-(pyridin-4-yl)prop-2-enoyl]phenyl 4-alkyloxybenzoates comprising an ester–chalcone central linkage and a pyridyl core. Members of the homologous series containing C12 alkyl chains or longer (i.e., C14 and C16) exhibited liquid crystalline behaviour in which the SmA phase was observed. Therefore, it can be concluded that the current core system requires a specific alkyloxy chain length ($n \geq 12$) to produce a smectic phase. The length of the terminal alkyloxy chain affects

the melting and clearing temperatures as well as the mesophase ranges. In our future work, molecular modifications will be carried out on this homologous series to yield liquid crystalline compounds with high thermal stabilities and wider mesophase ranges.

Acknowledgements

The authors would like to thank Universiti Tunku Abdul Rahman for the research facilities and financial support through UTAR Research Fund (Project No. IPSR/RMC/UTARRF/2014-C1/H01 with the Vote No. 6200/H21).

References

- [1] D. Adam, F. Closs, T. Frey, D. Funhoff, D. Haarer, H. Ringsdorf, P. Schuhmacher, K. Siemensmeyer, Transient photoconductivity in a discotic liquid crystal, *Phys. Rev. Lett.* 70 (1993) 457–460.
- [2] M.R. Huang, X.G. Li, J. Wang, Liquid crystalline polyaniline and its derivatives, *Tongji Daxue Xuebao* (in Chinese) 31 (2003) 848–852.

- [3] X.G. Li, M.R. Huang, W. Duan, Y.L. Yang, Novel multifunctional polymers from aromatic diamines by oxidative polymerizations, *Chem. Rev.* 102 (2002) 2925–3030.
- [4] X.G. Li, Q.F. Lu, M.R. Huang, Self-stabilized nanoparticles of intrinsically conducting co-polymers from 5-sulfonic-2-anisidine, *Small* 4 (2008) 1201–1209.
- [5] X.G. Li, M.R. Huang, Facile optimal synthesis of inherently electroconductive polythiophene nanoparticles, *Chem. Eur. J.* 15 (2009) 6446–6455.
- [6] W. Pisula, M. Zorn, J.Y. Chang, K. Mullen, R. Zentel, Liquid crystalline ordering and charge transport in semiconducting materials, *Macromol. Rapid Commun.* 30 (2009) 1179–1202.
- [7] B.P. Chandra, N. Periasamy, J.N. Das, Triboluminescence, a new tool to investigate fracture-initiation time of crystals under stress, *Pramana* 8 (1977) 395–401.
- [8] M. Funahashi, J. Hanna, Fast hole transport in a new calamitic liquid crystal of 2-(4'-heptyloxyphenyl)-6-dodecylthiobenzothiazole, *Phys. Rev. Lett.* 78 (1997) 2184–2187.
- [9] A. Ohno, A. Haruyama, K. Kurotaki, J. Hanna, Charge-carrier transport in smectic mesophases of biphenyls, *J. Appl. Phys.* 102 (2007) 083711.
- [10] S.T. Ha, T.M. Koh, H.C. Lin, G.Y. Yeap, Y.F. Win, S.T. Ong, Y. Sivasothy, L.K. Ong, Heterocyclic benzothiazole-based liquid crystals: synthesis and mesomorphic, *Liq. Cryst.* 36 (2009) 917–925.
- [11] S.T. Ha, T.M. Koh, S.T. Ong, Y. Sivasothy, Synthesis and mesomorphic behavior of benzothiazole-based liquid crystals having terminal methoxyl group, *Chin. Chem. Lett.* 20 (2009) 1449–1452.
- [12] S.T. Ha, T.M. Koh, G.Y. Yeap, H.C. Lin, S.L. Lee, Y.F. Win, S.T. Ong, Mesogenic Schiff base esters with benzothiazole core: synthesis and phase transition studies, *Phase Transit.* 83 (2010) 195–204.
- [13] T.M. Koh, S.T. Ha, G.Y. Yeap, H.C. Lin, New mesomorphic benzothiazoyl derivatives: synthesis and characterization, *Chin. Chem. Lett.* 24 (2013) 926–928.
- [14] L.L. Lai, C.H. Wang, W.P. Hsien, H.C. Lin, Synthesis and characterization of liquid crystalline molecules containing the quinoline unit, *Mol. Cryst. Liq. Cryst.* 287 (1996) 177–181.
- [15] N.K. Chudgar, S.N. Shah, New fluorescent mesogens with a chalcone central linkage, *Liq. Cryst.* 4 (1989) 661–668.
- [16] G.Y. Yeap, I. Susanti, B.S. Teoh, W.A.K. Mahmood, W.T.A. Harrison, Synthesis and phase transition in new chalcone derivatives: crystal structure of 1-phenyl-3-(4'-undecylcarbonyloxyphenyl)-2-propen-1-one, *Mol. Cryst. Liq. Cryst.* 442 (2005) 133–146.
- [17] B.T. Thaker, P.H. Patel, A.D. Vansadiya, J.B. Kanojiya, Substitution effects on the liquid crystalline properties of thermotropic liquid crystals containing Schiff base Chalcone linkages, *Mol. Cryst. Liq. Cryst.* 515 (2009) 135–147.
- [18] D. Demus, L. Richter, *Textures of Liquid Crystals*, Verlag Chemie, New York, 1978.
- [19] I. Dierking, *Textures of Liquid Crystals*, Wiley-VCH, Weinheim, 2003.
- [20] S.T. Ha, Y.W. Low, Synthesis and phase transition behaviors of new chalcone derivatives, *J. Chem. (Hindawi)* (2013), article ID 943723.
- [21] O.N. Kadkin, H. Han, Y.G. Galyametdinov, Synthesis, computational modelling and liquid crystalline properties of some [3]ferrocenophane-containing Schiff's bases and β -aminovinylketone: molecular geometry–phase behaviour relationship, *J. Organometall. Chem.* 692 (2007) 5571–5582.
- [22] S.T. Ha, K.L. Foo, R.T. Subramaniam, M.M. Ito, S.S. Sastry, S.T. Ong, Heterocyclic benzoxazole-based liquid crystals: synthesis and mesomorphic properties, *Chin. Chem. Lett.* 22 (2011) 1191–1194.
- [23] G. Sangameswari, N.P.S. Prabu, M.L.N.M. Mohan, Binary mixtures of hydrogen-bonded ferroelectric liquid crystals: thermal span enhancement in Smectic X* phase, *Zeitschrift für Naturforschung A* 70 (2015) 757–774.
- [24] A. Martínez-Felipe, C.T. Imrie, The role of hydrogen bonding in the phase behaviour of supramolecular liquid crystal dimers, *J. Mol. Struct.* 1100 (2015) 429–437.
- [25] J.H. Lee, S.J. Lee, J.Y. Jho, Room temperature supramolecular columnar liquid crystals formed by hydrogen bonding of isoquinoline derivatives, *Phase Trans.* 87 (2014) 656–665.
- [26] M.D. Miranda, F.V. Chávez, T.M.R. Maria, M.E.S. Eusebio, P.J. Sebastião, M.R. Silva, Self-assembled liquid crystals by hydrogen bonding between bipyridyl and alkylbenzoic acids: solvent-free synthesis by mechanochemistry, *Liq. Cryst.* 41 (2014) 1743–1751.
- [27] G.W. Gray, *Molecular Structure and Properties of Liquid Crystals*, Academic Press, London, 1962.
- [28] P. Berdague, J.P. Bayle, M.S. Ho, B.M. Fung, New laterally aromatic branched liquid crystal materials with large nematic ranges, *Liq. Cryst.* 14 (1993) 667–674.